



CHARACTERIZING AND EVALUATING COMBINED ELECTRODES-ELECTROLYTE CERAMICS FOR HIGH AND INTERMEDIATE TEMPERATURE SOFC¹

Taisa Eva Fuziger Gutierrez²

Roberto Furtado³

Raquel Furtado³

Rodrigo Dias⁴

Roberta Martins de Santana⁴

Glauco Rigueira⁵

José Geraldo de Melo Furtado⁶

Abstract

This work aims to characterize and evaluate the structural characteristic of combined electrodes-electrolyte ceramic with main focus on the analysis performed by microscopy techniques, X-ray diffraction and fluorescence analysis. The results show on one hand the importance of uniformity of porous electrodes, and on the other hand, the high densification level and physical-chemical homogeneity of the electrolyte to the macroscopic electric performance of the device. The influence of bulk, interface and surface physical-chemical characteristics were analyzed and discussed based on experimental results and theoretical examples.

Key words: Fuel cells; Solid electrolyte; Electrolyte-electrode assembly.

CARACTERIZANDO E AVALIANDO CONJUGADOS CERÂMICOS ELETRODOS-ELETRÓLITO PARA CÉLULAS A COMBUSTÍVEL DE ÓXIDO SÓLIDO DE ALTA E DE INTERMEDIÁRIA TEMPERATURA DE OPERAÇÃO

Resumo

Este trabalho tem como objetivo caracterizar e avaliar as características estruturais de conjugados cerâmicos eletrólito-eletrodos com base em análises microscópicas, difração e fluorescência de raios-X. Os resultados mostram a importância da elevada densificação e da homogeneidade físico-química do eletrólito para o desempenho do dispositivo. As influências de características massivas, superficiais e de interface foram analisadas e discutidas com base em resultados experimentais e exemplos teóricos.

Palavras-chave: Células a combustível; Eletrólito sólido; Eletrólito-eletrodos.

¹ Technical contribution to 66th ABM Annual Congress, July, 18th to 22th, 2011, São Paulo, SP, Brazil.

² M.Sc., Researcher, Special Technologies Department (DTE), Electric Power Research Center, CEPEL, P.O.Box 68007, 21940-970, Rio de Janeiro, Brazil. e-mail: taisa_fuziger@yahoo.com.br

³ B.Sc., Juiz de Fora Federal University.

⁴ B.Sc., CEPEL.

⁵ M.Sc., CEPEL.

⁶ D.Sc., CEPEL.

1 INTRODUCTION

Fuel cells are electrochemical devices that via electrochemical reactions are able to combine a fuel and an oxidant, converting the stored chemical energy of the fuel directly into direct-current electrical energy and heat. The fuel is not burned, such as in a flame, as in conventional power systems; rather, it is electrochemically oxidized. Thus, the maximum efficiency of a fuel cell is not limited by the Carnot cycle, which limits many conventional power systems such as the internal combustion engines, steam and gas turbines, and heat pumps.⁽¹⁾ Thus, fuel cells have been regarded as the main power generation equipment capable of increasing the energy conversion efficiency in various fields of applications.^(2,3)

Solid oxide fuel cell (SOFC), one of the types of fuel cells, is one of the most promising technologies for the production of energy, with potential to be a typical future distributed cogeneration system^(4,5) due to its high energy efficiency, low pollutant emissions, potential fuel flexibility, high modularity as a solid-state device and co-generation capability.^(5,6) Typically, a SOFC system is constituted of at least seven distinct components:⁽⁶⁻⁸⁾ fuel feed, anode, electrolyte media (separating the two electrodes), cathode, oxidant agent feed (normally air), and electrical interconnectors (completing the electrical circuit) as schematically showed in the Figure 1.

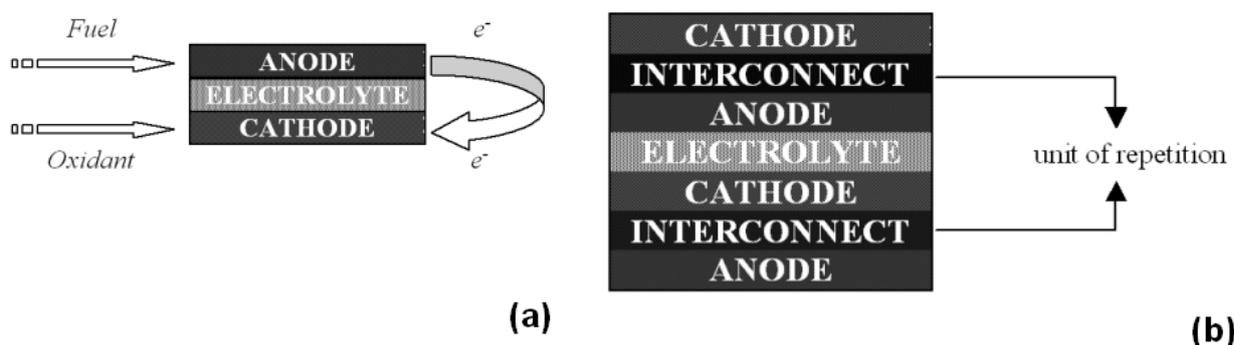


Figure 1. (a) Schematic diagram of a fuel cell; (b) scheme of the connection of the anode of a single fuel cell to the cathode of the subsequent single fuel cell, constituting a solid oxide fuel cell stack.

In SOFC technology, the heart of the fuel cell is a solid-state composite material-device of which emerges the respective electrical fuel cell behavior. This composite component is the Electrolyte-Electrodes Assembly (EEA), also known as MEA (Membrane Electrode Assembly), which is composed by a solid electrolyte sandwiched by two electrocatalysts-porous-electrodes, becoming the main component that holding the most significant influence on overall cost, useful life and fuel cell performance.⁽⁸⁻¹⁰⁾ Technologically there is a greater tendency to develop the planar configuration for SOFC systems, and this type of configuration is capable of achieving very high power density,^(8,11) characterized by a very thin electrolyte deposited on an anode considerably thicker, but that presents a reaction zone typically five to six times thicker than the electrolyte.^(6,11) Thus, the electrolyte contribution to the ohmic loss is minimized and the microstructural characteristics of the interfacial electrolyte/anode region become highly relevant to determining the electrical behavior of SOFC. Accordingly, this work aims to characterize and evaluate the structural characteristic of combined electrodes-electrolyte ceramic with main

focus on the analysis performed by microscopy techniques, X-ray diffraction and fluorescence analysis, within a research line of the CEPEL (Electric Power Research Center, Brazil), as a contribution to the characterization and understanding of the behaviour of these systems.

2 EXPERIMENTAL

In this work studies were performed with systems electrolyte/anode 8YSZ/Ni-YSZ and ERC/NiO, where ERC is rare-earth-doped ceria (RedCe) and 8YSZ is yttria-(8mol%)-stabilized zirconia, which are the electrolytes that have been considered for SOFC applications of high and intermediate temperature. The respective ceramic electrolyte powders were synthesized and applied to the anode structures.

For the synthesis of 8mol%Y₂O₃-stabilized zirconia (8YSZ) powder, by Pechini's method, the zirconium oxychloride octahydrate (ZrOCl₂.8H₂O) and the yttrium nitrate pentahydrate (Y(NO₃)₃.5H₂O) were dissolved in ethylene glycol, anhydrous citric acid was added in a molar ratio of 1:5 between ethylene glycol and citric acid. The mixture was stirred for about 30 minutes under heating to 80°C, to promote polyesterification. The resulting gel was kept in oven at 180°C for 12 hours. The resulting fine powders were calcined at 900°C for 6h using heating rates of 10°C/min, with air flow rate of 60 mL/min. The ERC system was obtained from acid digestion of praseodymium, dysprosium and yttrium oxides under stirring at 70°C for 48 hours and subsequent them infiltration into the matrix of ceria powder, heated to 120°C and stirring for 24 hours. Suspensions of the respective powders were prepared and deposited by tape casting (8YSZ) and by filtering (ERC) on the respective anode materials. The systems were sintered and prepared for characterization. Crystalline phases were detected by X-ray diffraction (XRD) analysis with a PANalytical X'Pert PRO diffractometer using Cu K α -radiation ($\lambda = 1.541806\text{\AA}$) with Ni filter and the data were collected from 20° to 100°. The microstructures of the samples were examined by scanning electron microscopy (SEM, Jeol JSM-64602 LV) equipped with X-ray dispersive energy spectroscopy (EDS, Link ISIS, Oxford Instruments) for chemical compositional analysis. The electrothermal behavior was measured using a curve tracer source-measurement unit (Tektronix 577).

3 RESULTS AND DISCUSSION

Figure 2 shows photomicrographs of the 8YSZ/Ni-YSZ combined anode electrode-electrolyte ceramic. Both in the Figure 2(a) as in Figure 2(b) it were clearly identifies the regions of the electrolyte and of the anode as a function of their characteristic aspects of the consolidated materials are very different, since the anode is essentially porous, while the electrolyte is essentially dense. In fact, according to the photomicrograph shown in Figure 2 (b) it was observed the porous structure of anode and electrolyte microstructures showing clear grain boundaries as a result of high densification, although intra- and mainly intergranular pores are observed, which can be reduced or eliminated by optimizing the sintering. In Figure 1 (a), secondary electrons image, it was note the dimensions involved and, in this case, the thickness of electrolyte is about twenty times lower than that of the anode. The microstructural characteristics of the interface electrolyte/anode can also be examined from the photomicrograph of Figure 2(b), backscattered electrons image, in which it appears that although there is some heterogeneity, there was no

interpenetration between the layers. Figure 3 shows the EDS spectrum characteristic of ceramic combined system shown in Figure 2, showing, as expected, only the presence of Zr, Y and Ni.

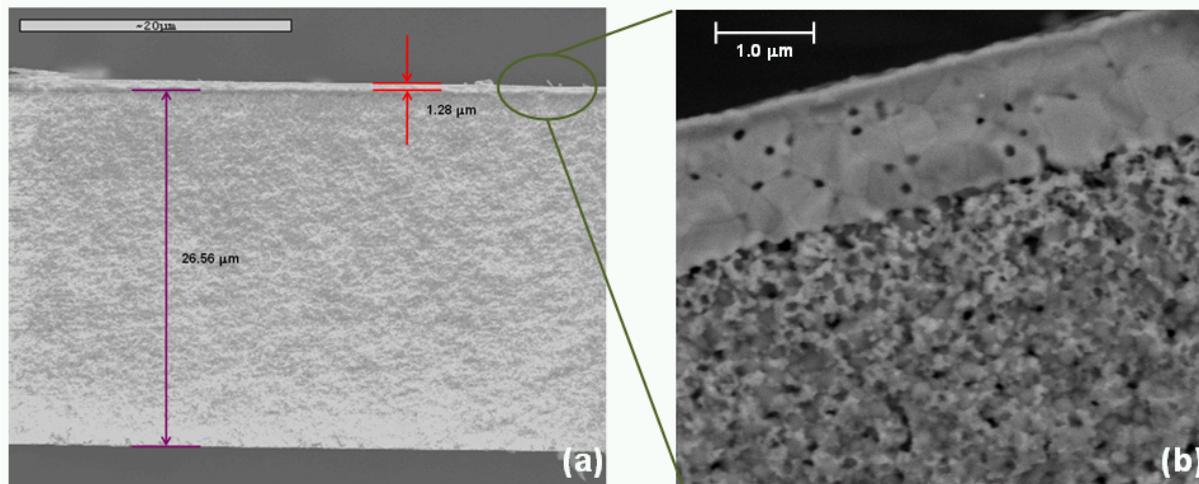


Figure 2. SEM photomicrographs: (a) secondary electrons image - 8YSZ/Ni-YSZ combined anode electrode-electrolyte ceramic sample; (b) backscattered electrons image - amplified region showing the 8YSZ/Ni-YSZ interface and the anode reaction zone.

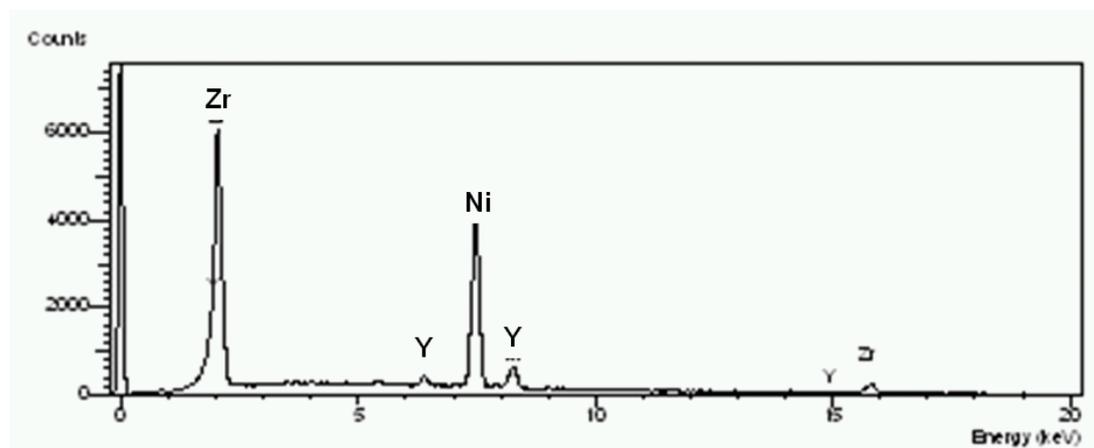


Figure 3. X-ray dispersive energy spectroscopy (EDS) spectrum characteristic of ceramic combined system shown in Figure 2.

The results of a detailed microanalysis EDS can be seen in Figure 4, where the composition is chemically analyzed along the yellow line shown on the photomicrography and beginning at a point located within the grain of 8YSZ and ends in the anodic region already distant of the 8YSZ/electrode interface, but yet the typical reaction zone. The EDS spectra along said line, for the elements Zr, Y and Ni are shown respectively in Figures 4 (b), (c) and (d) and the results indicate the absence of interpenetration, since Ni essentially it was not detected in the area of the electrolyte (Figure 4 (d)), which presents a partially complementary to the profile of Zr (Figure 4 (b)). After the interface electrolyte/electrode count on Ni is considerably high and, based on the image obtained with backscattered electrons (Figure 4 (a)) it was noted that the Ni is well dispersed in the reaction zone. On the other hand, the Y has a profile of amphoteric character, since it is found at comparable levels (slightly higher in the area of the electrolyte) on both sides of the interface electrolyte/anode. The absence of interpenetration of Ni is an indication of

suitable conditions of processing, but still need some optimization in order to reduce the porosity remaining in the electrolyte, because on the one hand, as noted by Nakajo et al.⁽¹²⁾ the diffusion of Ni into the electrolyte can lead to failures of SOFC at high temperatures and, on the other hand, porosity is a factor that results in loss of efficiency of the electrolyte.^(6,10)

The microstructure of the anode can also be best seen in the photomicrographs shown in Figure 5, which show the porous nature of the structure, which is essential to ensure the percolation of gas and the establishment of the triple-phase region,⁽⁶⁾ still providing thermal stability to the device.⁽¹³⁾

In fact, the characteristics of the transition region between the porous anode and dense electrolyte that ultimately characterize the interface 8YSZ/Ni-YSZ, are critical to ensure performance and stability for a SOFC.^(12,13) It should ensure that there is electrical connection available for ionic transport in this interface, without the existence of discontinuities that result in the establishment of impedances.^(6,14) In this sense, the high densification of the electrolyte is essential.^(12,15,16) Particularly in the photomicrographs of Figure 6 to identify clear grain boundaries, although in Figure 6(a) it is possible to identify any inter-and intragranular porosity, as seen in Figures 2(b) and 4(a). Since Figure 6(b) shows the absence of porosity and average grain size slightly less than the characteristic of Figure 6(a). The EDS spectrum shown in Figure 6(c) is associated with the photomicrograph of Figure 6(b) and indicates, as expected, only the elemental composition of the electrolyte, without contamination by Ni.

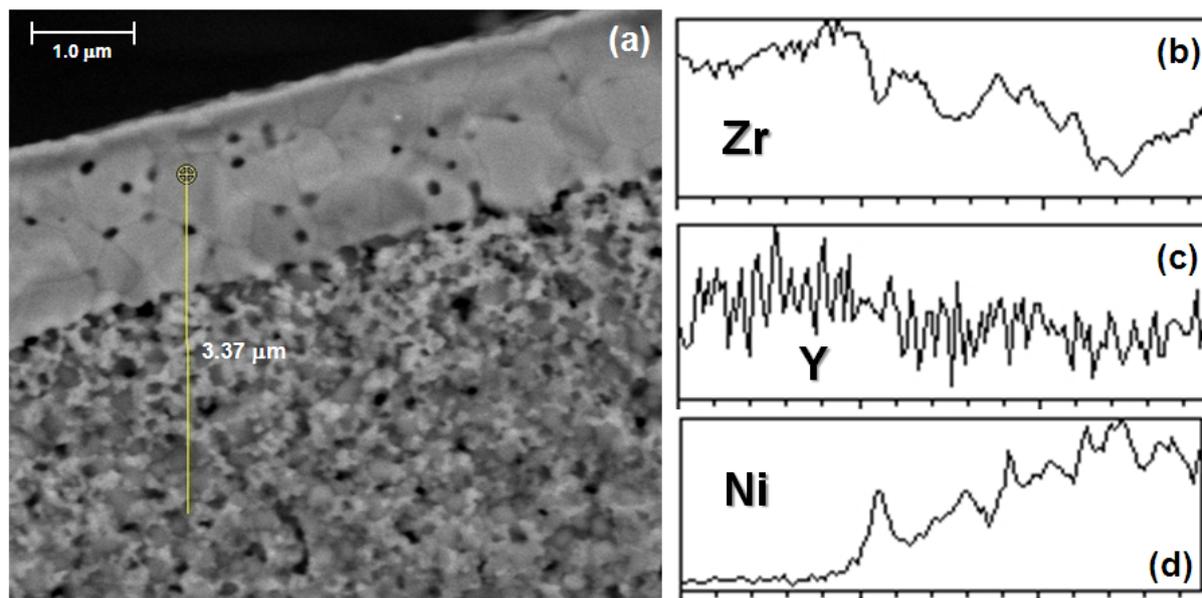


Figure 4. SEM-EDS Analysis: (a) backscattered electrons image - amplified region (Figure 2(b)) showing the 8YSZ/Ni-YSZ interface and the anode reaction zone, as well as the yellow line where EDS analysis was carried out; EDS spectrum for (b) Zr, (c) Y, and (d) Ni.

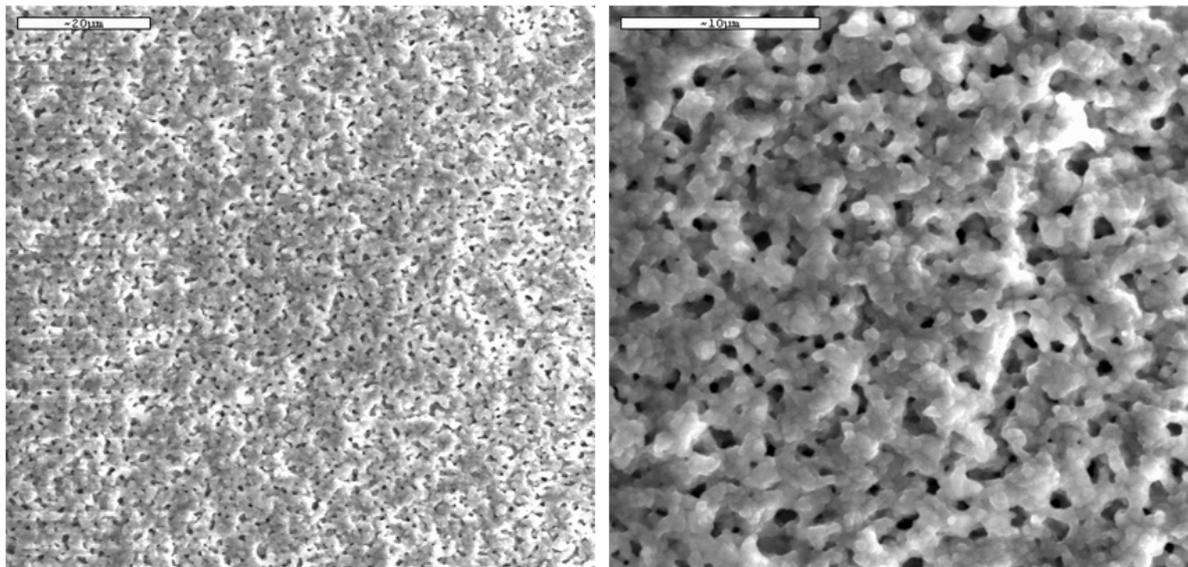


Figure 5. SEM photomicrographs (secondary electrons image) of the anodic electrode of the combined electrodes-electrolyte ceramic.

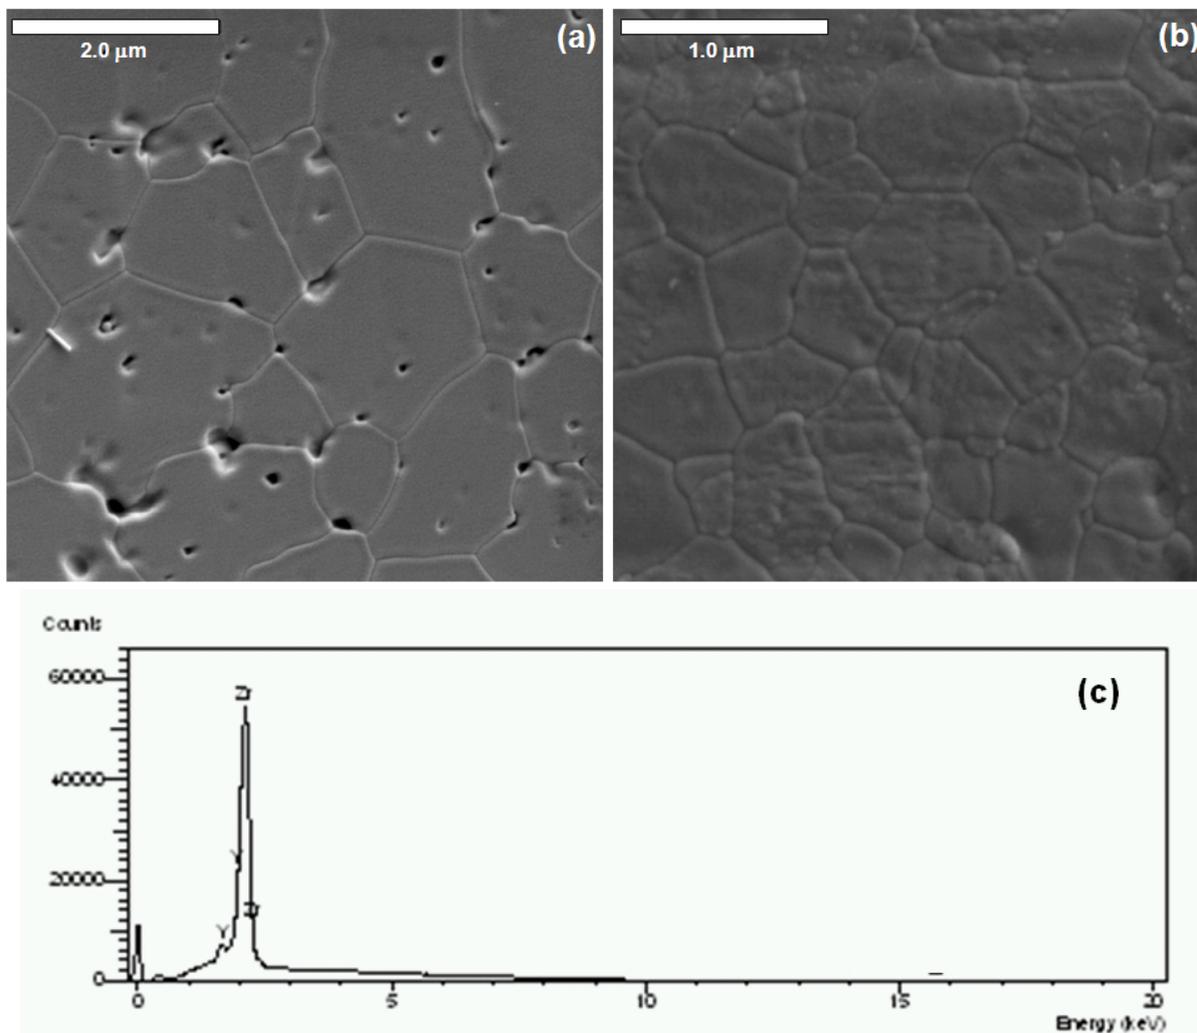


Figure 6. SEM micrographs of 8YSZ specimens sintered in different conditions: (a) showing mainly intergranular porosity; (b) showing a fully densified microstructure; (c) overall characteristic EDS spectrum.

In researches that have been developed in Cepel the focus has been the characterization and evaluation of electrolytes and electrode / electrolyte interface, as well as studies of processing to obtain highly densified electrolyte as shown in the photomicrographs of Figures 6(b), 7(a) and 7(b). To mount the unit cells have been used commercial cathode, which like the anode must have porous structure. Figure 7(c) shows a typical photomicrograph of the microstructure of SOFC cathodes.

Besides the traditional 8YSZ electrolyte, we have been also worked with electrolyte in the production of alternative combined electrode-electrolyte for application in intermediate temperature SOFC. Figure 8 shows a photomicrograph of the microstructure of a combined ERC/NiO and its chemical analysis by EDS of the electrolyte layer. The microstructure shows a distribution of porosity increasing from top to bottom, once the top layer is the electrolyte.

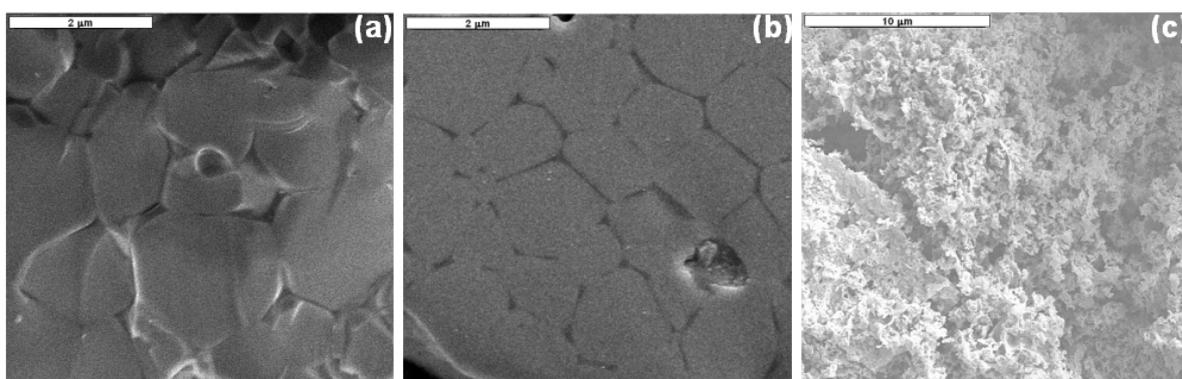


Figure 7. SOFC material microstructures: (a) and (b) full-densified YSZ ceramic; (c) porosity cathode ceramic.

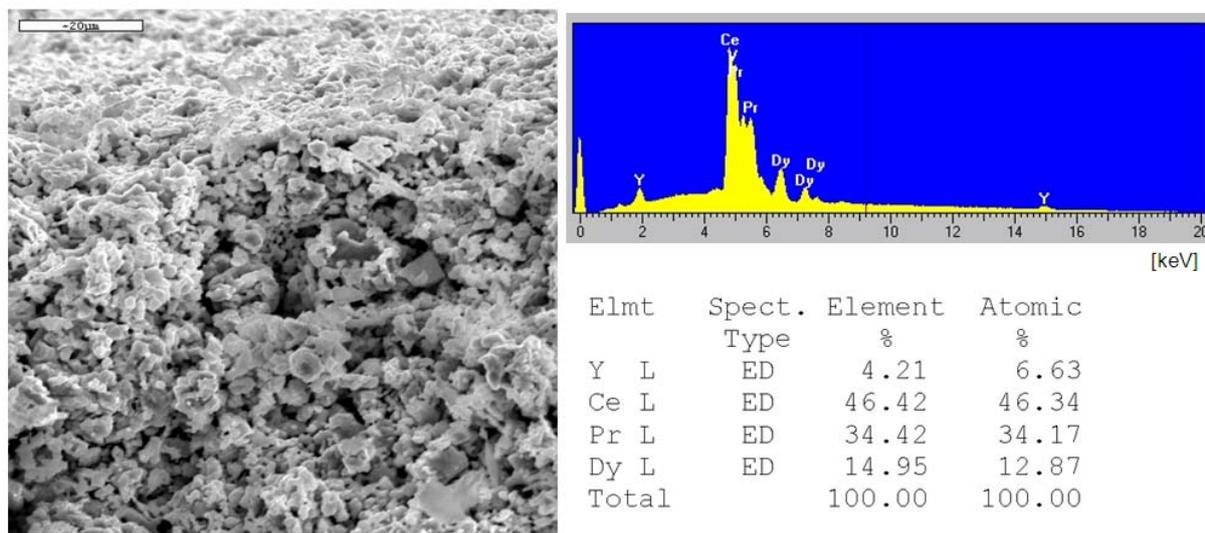


Figure 8. SEM micrographs of ERC/NiO combined bilayer and electrolyte layer characteristic EDS spectrum.

Figure 9 shows the X-ray diffraction patterns of the two electrolytes synthesized in this work and used in the preparation of the respective combined electrodes-electrolyte ceramics. For 8YSZ sample are identified characteristic peaks of cubic fluorite type structure and for the sample RedCe the peaks are characteristic of the

solid solution of ceria and yttria doped with praseodymium (0.144 mol) and dysprosium (0.346 mol).

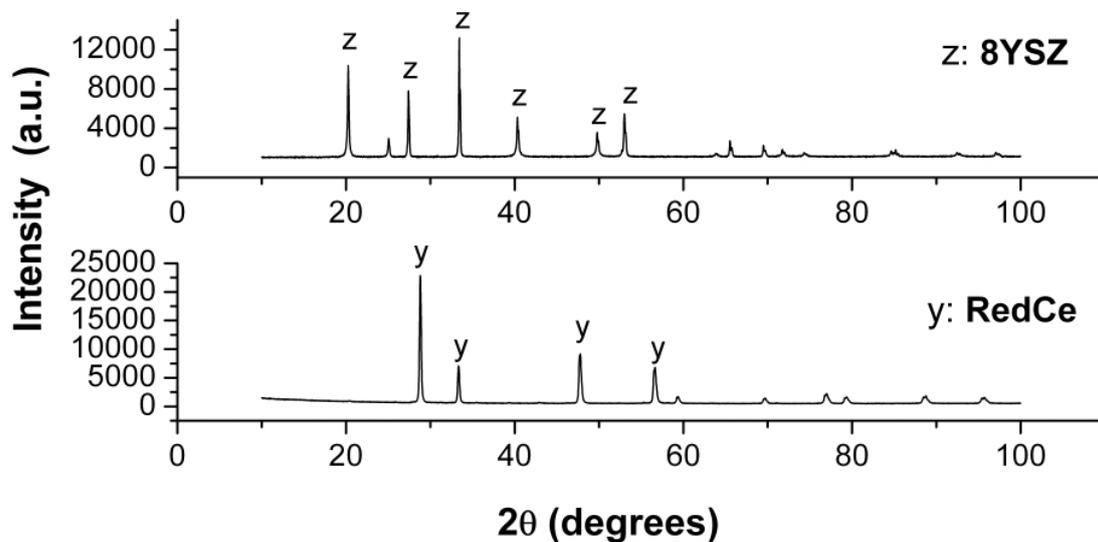


Figure 9. X-ray diffraction patterns of the studied electrolyte ceramics.

Figure 10 shows the results of ionic conductivity of both electrolytes studied and Figure 11 shows the results of total electrical conductivity of the combined electrode-electrolyte ceramics evaluated.

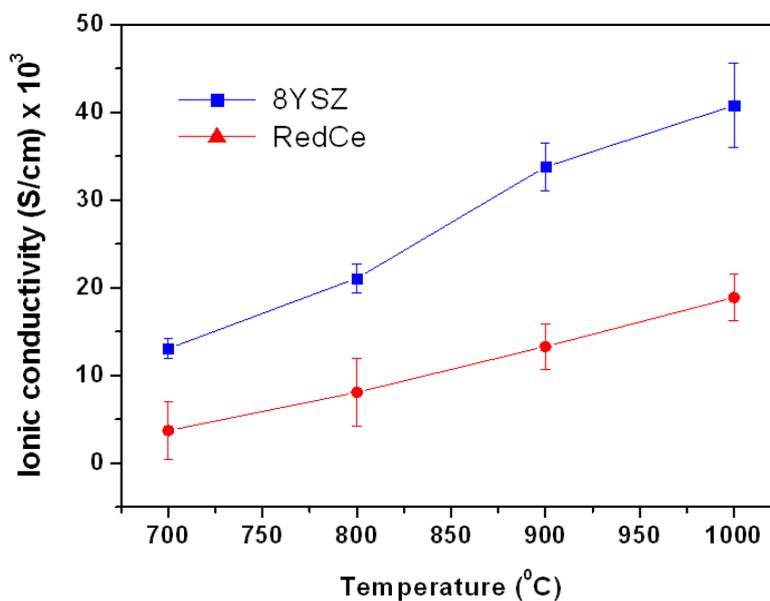


Figure 10. Ionic conductivity of the electrolyte ceramics studied as a function of temperature in the range of 700 to 1000°C.

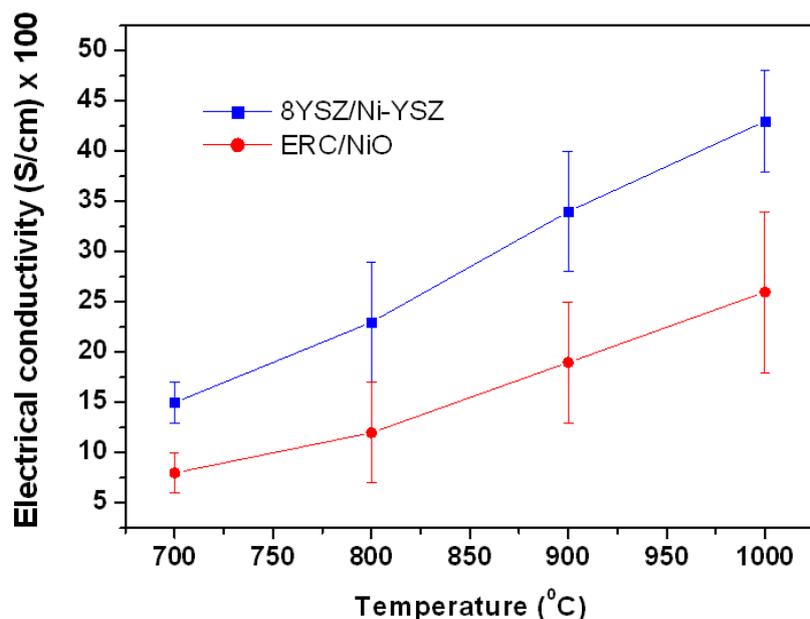


Figure 11. Total electrical conductivity of the electrolyte ceramics studied as a function of temperature in the range of 700 to 1000°C.

These electrothermal characterization results (Figures 10 and 11) show that the difference in ionic conductivity between the two electrolytes is higher for temperatures above 850°C, although, for the case studied, the ionic conductivity of 8YSZ are much larger along the entire temperature range, which is certainly a reflection of their greater degree of densification, since the samples based on ceria could not reach the same level of densification. This also seems to be responsible for the variability of the values of ionic conductivity of ceria electrolyte.

In fact, this behavior is also similar to the total electrical conductivity of the conjugate shown in Figure 11. In this case, the relative difference is smaller, but the variability is significant, particularly for the system ERC/NiO. As can be seen by comparing the microstructures shown in Figures 2 and 8 this latter system provides greater porosity and microstructural heterogeneity, which were reflected on its electrical characteristics, contributing greatly to the reduction of transport properties of electric charge. The fact that the system ERC/NiO has been produced by the filtration technique, due to its microstructure, shows that this process is not yet optimized, which incidentally also occurs, although to a lesser extent, with the production system 8YSZ/Ni by tape casting. Indeed, studies have now developed aimed at improving production techniques of these combined electrodes-electrolyte ceramics.

4 CONCLUSIONS

This work presented results of microstructural and electrical characterization of combined electrodes-electrolyte ceramics for application in solid oxide fuel cells. The main objective of the research with these materials and devices is to produce more homogeneous and fully densified electrolyte ceramic microstructure and electrodes with uniformly distributed porosity and high electrocatalytic activity, which will result in fuel cells with better electrical performance and higher electrothermal stability. Accordingly, were produced and characterized combined electrodes-electrolyte by tape casting and filtration method. The results showed the establishment of 8YSZ-Ni interface and anodic reaction zone conditions that suggests by microstructural



evaluation be very close to the adequate, which is corroborated by the results of electrothermal characterization. Moreover, obtaining CER/NiO conjugate was more difficult and process improvements should be implemented in the future.

REFERENCES

- 1 FAGHRI, A. Unresolved Issues in Fuel Cell Modeling. **Heat Transfer Engineering**, v.27, p. 1-3, 2006.
- 2 HOFFERT, M. I. Energy implications of future stabilization of atmospheric CO₂ content. **Nature**, v.395, p. 881-884, 1998.
- 3 CRABTREE, G. W., DRESSLHAUS, M. S., BUCHANAN, M. V. The Hydrogen Economy. **Physics Today**, Dec, 2004.
- 4 NEEF, H.-J. International overview of hydrogen and fuel cell research. **Energy**, V. 34, p. 327-333, March 2009.
- 5 ZINK, F., LU, Y., SCHAEFER, L. A solid oxide fuel cell system for buildings. **Energy Conversion and Management**, V. 48, p. 809-818, March 2007.
- 6 MINH, N. Q. Solid Oxide Fuel Cell Technology-Features and Applications, **Solid State Ionics**, v. 174. p. 271-277, 2004.
- 7 WINCEWICZ, K. C., COOPER, J. S. Taxonomies of SOFC material and manufacturing alternatives. **Journal of Power Sources**, 140, p.280-296, 2005.
- 8 SINGHAL, S. C., KENDALL, K. High temperature Solid Oxide Fuel Cells: Fundamentals, Design and Applications, Oxford, UK: Elsevier Ltd., p. 405, 2003.
- 9 IVERS-TIFFÉE, E., WEBER, A., SCHMID, K., KREBS, V. Macroscale modeling of cathode formation in SOFC. **Solid State Ionics**, v.174, n.1-4, p. 223-232, 2004.
- 10 STEELE, B. C. H., HEINZEL, A. Materials for fuel-cell technologies. **Nature**, v.414, p. 345-352, 2001.
- 11 HUSSAIN, M. M., LI, X., DINCER, I. A general electrolyte-electrode-assembly model for the performance characteristics of planar anode-supported solid oxide fuel cells. **Journal of Power Sources**, 189, p.916-928, 2009.
- 12 NAKAJO, A., WUILLEMIN, Z., VAN HERLE, J., FAVRAT, D. Simulation of thermal stresses in anode-supported solid oxide fuel cell stacks - Part I: Probability of failure of the cells. **Journal of Power Sources**, 193, p. 203-215, 2009.
- 13 PIHLATIE, M., KAISER, A., MOGENSEN, M. Redox stability of SOFC: Thermal analysis of Ni-YSZ composites. **Solid State Ionics**, v.180, n.17-19, p.1100-1112, 2009.
- 14 LAURENCIN, J., DELETTE, G., SICARDY, O., ROSINI, S., LEFEBVRE-JOUD, F. Impact of 'redox' cycles on performances of solid oxide fuel cells: Case of the electrolyte supported cells. **Journal of Power Sources**, v.195, n.9, p.2747-2753, 2010.
- 15 PÉREZ-COLL, D., SÁNCHEZ-LÓPEZ, E., MATHER, G. C. Influence of porosity on the bulk and grain-boundary electrical properties of Gd-doped ceria. **Solid State Ionics**, v.181, n. 21-22, p. 1033-1042, 2010.
- 16 LIU, Y.L., HAGEN, A., BARFOD, R., CHEN, M., WANG, H. J., POULSEN, F. W., HENDRIKSEN, P.V. Microstructural studies on degradation of interface between LSM-YSZ cathode and YSZ electrolyte in SOFCs. **Solid State Ionics**, v.180, n. 23-25, p. 1298-1304, 2009.