



## EFFECT OF TEMPERATURE AND PRESSURE ON WEAR PROPERTIES OF ION NITRIDED AISI 316 AND 409 STAINLESS STEELS<sup>1</sup>

Frederico Augusto Pires Fernandes<sup>2</sup>

Stênio Cristaldo Heck<sup>3</sup>

Ricardo Gomes Pereira<sup>4</sup>

Pedro Augusto de Paula Nascente<sup>5</sup>

Luiz Carlos Casteletti<sup>6</sup>

### Abstract

Stainless steels are widely used in chemical and other industries due to their corrosion resistance property. However, because of their low hardness and wear properties, their applications are limited. Many attempts have been made to increase the surface hardness of these materials by using plasma techniques. Plasma nitriding is distinguished by its effectiveness, and for presenting a relatively low cost and being a clean process, producing hard surface layers on stainless steels. Aiming to verify the influence of the temperature and pressure on the modified resultant layers, samples of AISI 316 and 409 stainless steels were plasma nitrided in two different temperatures (450 and 500°C) and pressures of 400, 500, and 600Pa for 5h. After the nitriding treatment, the layers were analyzed by means of optical microscopy and wear tests. Wear tests were conducted in a fixed-ball micro-wear machine without lubrication. After the plasma nitriding treatment on AISI 316 and 409 samples, homogeneous and continuous layers were produced and their thicknesses increased as the temperature increased, and as the pressure decreased. The nitriding treatment on the AISI 316 steel sample resulted on the formation of expanded austenite layers at 450°C, and chromium nitrides (CrN and Cr<sub>2</sub>N) phases at 500°C. The nitriding treatment on AISI 409 sample yielded the formation of similar layers for both treatment temperatures; these layers constituted mainly by chromium (Cr<sub>2</sub>N) and iron (Fe<sub>2</sub>N, Fe<sub>3</sub>N, and Fe<sub>4</sub>N) nitrides. After the nitriding treatment, the AISI 316 steel sample presented higher wear resistance for lower temperature and pressure values. The increase on layer fragility, for higher temperature and pressure values can be responsible for this inverse tendency. The wear resistance of the nitrided AISI 409 sample followed a logic tendency: the harder the layer the better the performance, i.e. the performance was improved with the increase in both the temperature and pressure.

**Key words:** Stainless steel; Plasma nitriding; Wear.

## EFfeito DA TEMPERATURA E PRESSÃO NO DEsgASTE DOS AÇOS AISI 316 E 409 NITRETADOS IONICAMENTE

### Resumo

Os aços inoxidáveis são amplamente utilizados em indústrias químicas e várias outras devido à sua excelente resistência à corrosão. No entanto, devido a sua baixa dureza e propriedades de desgaste insatisfatórias suas aplicações são limitadas. Muitas tentativas são feitas no intuito de aumentar a dureza desses materiais, utilizando técnicas de plasma. A nitretação por plasma se distingue pela sua eficácia, por apresentar um custo relativamente baixo e ser um processo limpo, produzindo camadas superficiais duras em aços inoxidáveis. Com o objetivo de verificar a influência da temperatura e da pressão em camadas produzidas por nitretação, amostras dos aços inoxidáveis AISI 316 e 409 foram tratadas em duas temperaturas diferentes (450 e 500°C) e pressões de 400, 500 e 600Pa por 5h. Após o tratamento de nitretação por plasma as camadas foram analisadas por meio de microscopia óptica e testes de desgaste. Os testes de desgaste foram realizados em uma máquina de micro-desgaste, do tipo esfera presa, sem lubrificação. O tratamento de nitretação por plasma produziu camadas homogêneas e contínuas sobre os aços AISI 316 e 409, sendo que a espessura das camadas aumentou com o aumento da temperatura, e diminuição da pressão. Os tratamentos de nitretação nas amostras do aço AISI 316 resultaram na formação de camadas de austenita expandida a 450°C, e nitretos de cromo (CrN e Cr<sub>2</sub>N) a 500°C. Os tratamentos de nitretação no aço AISI 409 resultaram na formação de camadas semelhantes em ambas às temperaturas de tratamento, sendo constituídas principalmente por nitretos de cromo (Cr<sub>2</sub>N) e ferro (Fe<sub>2</sub>N, Fe<sub>3</sub>N e Fe<sub>4</sub>N). Após o tratamento de nitretação as amostras do aço AISI 316 apresentaram maior resistência ao desgaste para tratamentos realizados em menores temperaturas e pressões. O aumento na fragilidade da camada, para maiores valores de temperatura e pressão pode ser responsável por esta tendência inversa. A resistência ao desgaste das amostras do aço AISI 409 nitretado seguiram uma tendência lógica: quanto maior a dureza da camada, melhor o desempenho, ou seja, a resistência ao desgaste foi melhorada com o aumento na temperatura e pressão.

**Palavras chave:** Aços inoxidáveis; Nitretação por plasma; Desgaste.

<sup>1</sup> Technical contribution to the 18<sup>th</sup> IFHTSE Congress - International Federation for Heat Treatment and Surface Engineering, 2010 July 26-30<sup>th</sup>, Rio de Janeiro, RJ, Brazil.

<sup>2</sup> Chemical Engineer, Doctoral Student, EESC-USP, São Carlos, Brazil.

<sup>3</sup> Chemist, EESC-USP, São Carlos, Brazil.

<sup>4</sup> Degree in Sciences, EESC-USP, São Carlos, Brazil.

<sup>5</sup> Physicist, Professor, DEMA-UFSCar, São Carlos, Brazil.

<sup>6</sup> Materials Engineer, Professor, EESC-USP, São Carlos, Brazil.

## 1 INTRODUCTION

Stainless steels are an important class of ferrous alloys. In fact, the omnipresence of stainless steels in our daily life makes it impossible to enumerate their applications.<sup>[1,2]</sup> Their corrosion resistance is excellent whereas their hardness and wear resistance are relatively poor, limiting some of their industrial applications. Therefore many attempts have been made to increase the surface hardness and wear of this class of materials.

Low temperature plasma nitriding treatment of stainless steels provides an attractive process to improve their wear resistance without affecting their corrosion properties.<sup>[1-4]</sup> Lower temperature means lower cost, less distortion, and less surface roughening.<sup>[5]</sup> During this treatment, a very hard (greater than 1000HV) and corrosion resistant metastable phase, expanded austenite “ $\gamma_N$ ”, is formed at the surface of these steels.<sup>[6-8]</sup> This very promising coating can only be achieved if the treatment temperature is lower than 500°C.<sup>[3]</sup> Above 500°C, chromium atoms are removed from the austenitic structure resulting in the precipitation of CrN, compromising the corrosion properties.<sup>[9]</sup>

The expanded austenite is a metastable phase with a supersaturation of nitrogen which remains in solid solution.<sup>[9-11]</sup> This thin, precipitate-free layer of saturated interstitial solid solution possesses a good combination of mechanical, tribological, and corrosion properties.<sup>[11]</sup> The produced layers on ferritic steels are mainly constituted by iron and chromium nitrides.<sup>[12]</sup> The nature of the plasma nitrided layer on austenitic stainless steel, which is considerably different from those of the usual ferrite steels, is not completely understood yet.<sup>[13]</sup>

The purpose of the present work is to verify the influence of the treatment temperature and pressure on the morphology and wear properties of plasma nitrided AISI 316 and 409 stainless steels.

## 2 MATERIALS AND METHODS

The stainless steels investigated in this work are commercially available materials, and its chemical compositions are given in Table 1. The samples employed in this investigation were solubilized at 1050°C for 30min followed by water quenching.

**Table 1.** Chemical composition (wt%) of the employed steels

	<b>C</b>	<b>Cr</b>	<b>Ni</b>	<b>Mo</b>	<b>Mn</b>	<b>Si</b>	<b>Fe</b>
<b>AISI 316L</b>	0.028	17.06	10.48	2.44	1.49	0.53	Bal.
<b>AISI 409</b>	0.030	11.25	0.06	0.11	0.74	0.49	Bal.

Samples of AISI 316L and AISI 409 were prepared according to conventional metallographic techniques, and then were plasma nitrided. The samples were cleaned by argon sputtering (under working pressure and a temperature 50°C lesser than the nitriding temperature, for 30min) inside the plasma chamber. The plasma treatment was done using the direct current method with the following conditions: a gas mixture of 80 vol. % H<sub>2</sub> and 20 vol. % N<sub>2</sub>, pressure values of 400, 500, and 600Pa, temperature values of 450 and 500°C, and time period of 5h. Ion nitrided samples were analyzed by optical microscopy, measurements of microhardness, X-ray diffraction, and wear testing.

Microstructural analysis was carried out by means of a Zeiss Axiotech optical microscope using the interference contrast technique after etching the samples with

nitromuriatic acid. Brinell indentations were carried out on the surface of the nitrided samples to evaluate the indentation crack network aspect. The indentation was performed with a load of 15.625kg using a 2.5mm steel sphere, applying the load for 10s. Micro-wear tests were performed in a fixed ball machine type without the use of abrasive using a sphere of 25.4mm in diameter. The rotation speed and load were 500rpm and 2.45N, respectively. Consecutive wear scars were produced with test times of 5, 10, 15, and 20 min to obtain the volume loss curve. The removed volume ( $V$ ) of each wear crater and its depth ( $h$ ) were calculated according to the following equations:<sup>[14,15]</sup>


$$V \approx \frac{\pi \cdot d^4}{64 \cdot R}, \text{ for } d \ll R \quad (1)$$

$$h \approx \sqrt{\frac{V}{\pi \cdot R}}, \text{ for } h \ll R \quad (2)$$

where  $d$  is the scar diameter and  $R$  the sphere radius.

### 3 RESULTS AND DISCUSSION

Figure 1 presents the optical micrographs of the cross-section of plasma nitrided AISI 316 and 409 samples at 450 and 500°C for 5h of treatment and pressures of 400 and 600Pa.

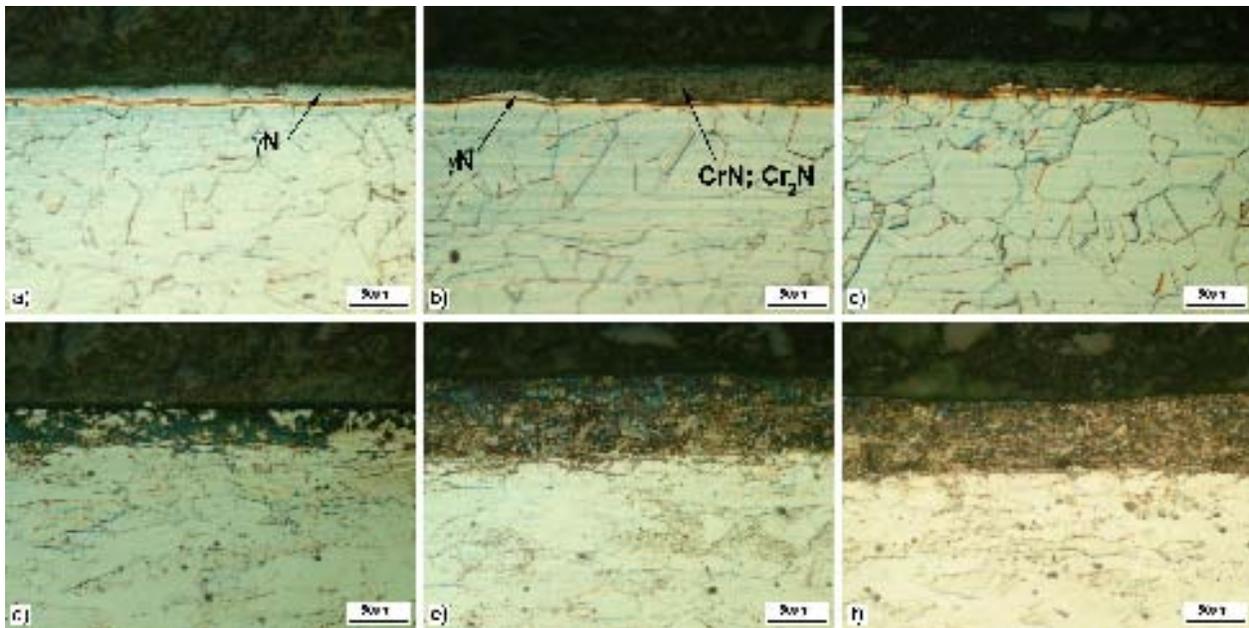


**Figure 1.** Optical cross section of nitrided samples: (a) AISI 316-450°C-400Pa; (b) AISI 316-500°C-400Pa; (c) AISI 316-500°C-600Pa; (d) AISI 409-450°C-400Pa; (e) AISI 409-500°C-400Pa; (f) 409-500°C-600Pa.

Fig. 1a shows a cross section of an AISI 316 sample nitrided at 450°C and 400Pa, in which the formed layer is constituted by expanded austenite and possibly the beginning of chromium nitrides precipitation, which are characteristic of low temperature

plasma nitriding (<math>500^{\circ}\text{C}</math>) of austenitic stainless steels. Increasing the temperature to  $500^{\circ}\text{C}$  (Fig. 1b), under the same pressure, the white expanded layer is replaced almost entirely by a dark chromium nitride layer that grew on top of the  $\gamma_{\text{N}}$  layer. The AISI 409 ferritic stainless steel presented the same layer constituent (mainly iron nitrides) for both  $450^{\circ}\text{C}$  (Fig. 1d) and  $500^{\circ}\text{C}$  (Fig. 1e) nitriding temperature. It was observed for both austenitic and ferritic steels that increasing nitriding temperature results in thicker layers.

Nitriding the AISI 316 and 409 steels under different pressures (400 and 600Pa) at the same temperature ( $500^{\circ}\text{C}$ ) resulted on a slightly decrease on layer thickness after increasing pressure (Figs. 1b and 1c for austenitic and Figs. 1e and 1f for ferritic stainless steel).

The X-ray diffraction patterns of the AISI 316 and 409 substrates and the plasma nitrided samples at different temperatures ( $450^{\circ}\text{C}$  and  $500^{\circ}\text{C}$ ) for 400Pa are presented in Figure 2. The untreated AISI 316 and 409 steels contain diffraction peaks related to the gamma ( $\gamma$ ) iron phase and ( $\alpha$ ) iron phase, which correspond to austenitic and ferritic stainless steels, respectively.

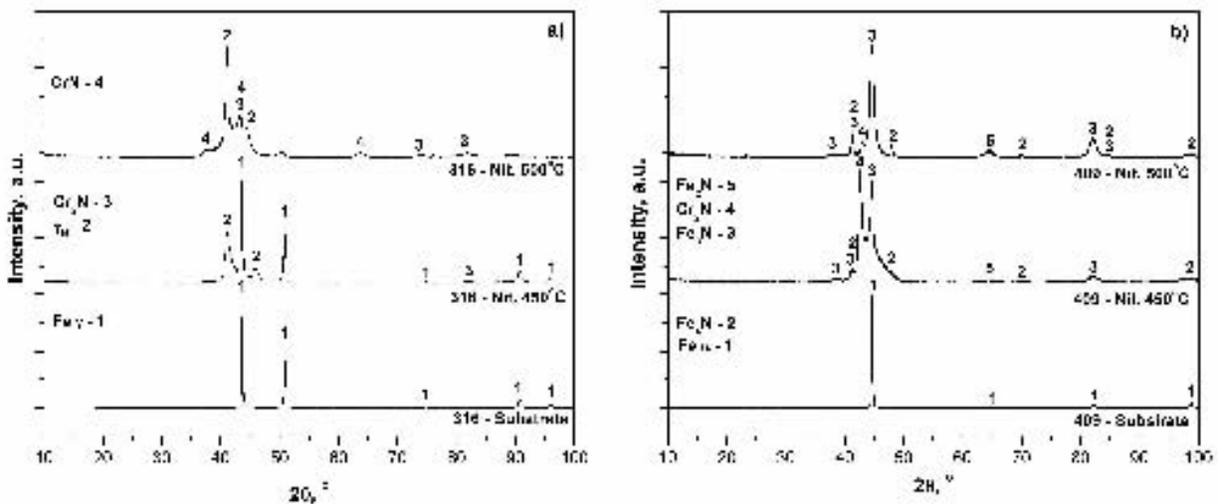

**Figure 2.** X-ray diffraction patterns of the non-nitrided and plasma nitrided samples of: (a) AISI 316; (b) AISI 409.

Nitriding the AISI 316 at  $450^{\circ}\text{C}$  (Fig. 2a) yielded the appearance of some diffraction peaks shifted to the left, which correspond to a nitrogen expanded austenite ( $\gamma_{\text{N}}$ ) phase. Also a peak related to  $\text{Cr}_2\text{N}$  appears, which indicates the beginning of the precipitation of chromium nitrides. At this temperature the layer is thin and the diffraction peaks of the substrate also appear. Further increase in nitriding temperature ( $500^{\circ}\text{C}$ ) maintain the expanded austenite diffraction peaks, and more  $\text{CrN}$  and  $\text{Cr}_2\text{N}$  peaks are detected, indicating clearly the precipitation of these nitrides. These findings confirm that the dark layer formed onto the white expanded austenite is a mixture of chromium nitrides.

The X-ray diffraction patterns of the plasma nitrided AISI 409 (Fig. 2b) shows, for both employed temperatures ( $450^{\circ}\text{C}$  and  $500^{\circ}\text{C}$ ), a mixture of chromium ( $\text{Cr}_2\text{N}$ ) and iron ( $\text{Fe}_2\text{N}$ ,  $\text{Fe}_3\text{N}$ , and  $\text{Fe}_4\text{N}$ ) nitrides. No expanded phase but rather a compound layer and/or precipitates were formed, which are in agreement with the literature.<sup>[11]</sup>

The thicknesses of the layers, obtained by direct measurements using optical micrographs, versus nitriding pressure for AISI 316 and 409 samples are plotted in

Figure 3, which clearly shows that the thicknesses of the layers are superior for the AISI 409 sample compared to the AISI 316 sample for both temperatures. However, an inverse effect was observed when plotting layer thickness versus nitriding pressure, showing that the thickness slightly decays for both steels at both temperatures.

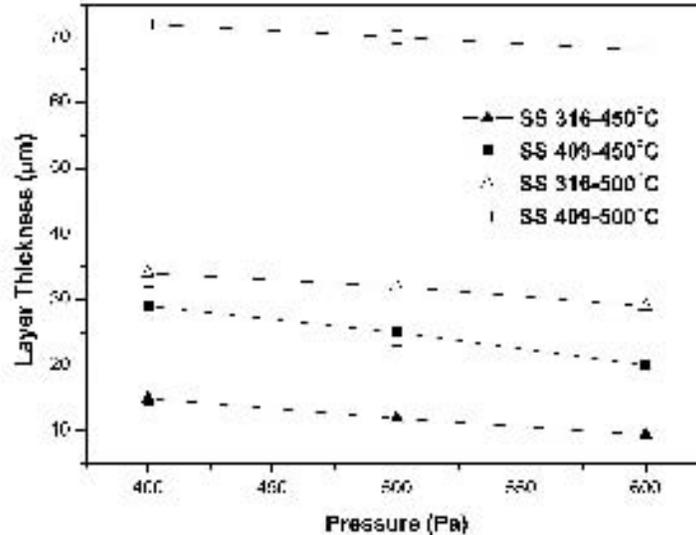


Figure 3. Layer thickness versus nitriding pressure, of plasma nitrided AISI 316 and 409.

Figure 4 presents the wear volume loss curves after tribological characterization in dry sliding for the AISI 316 and 409 samples nitrided at 450 and 500°C under 400 and 600Pa.

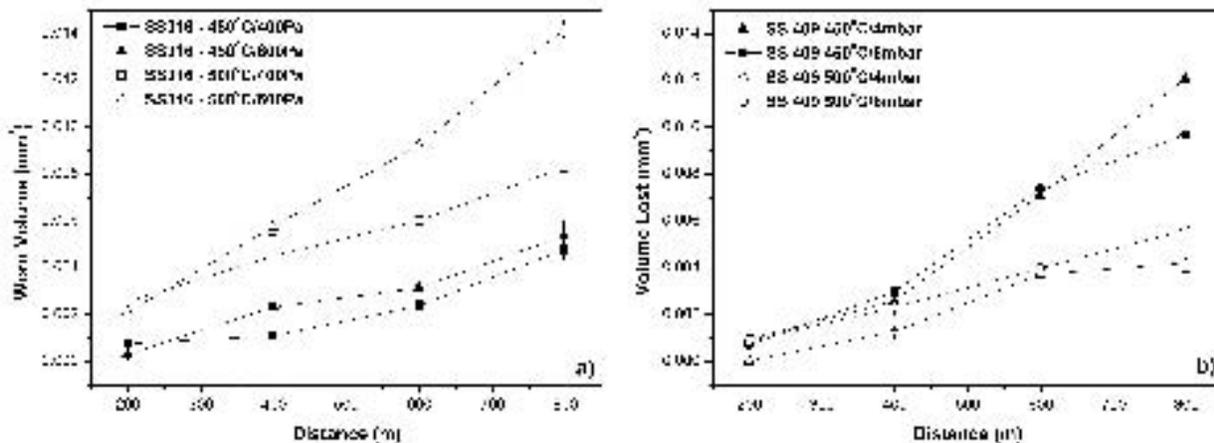



Figure 4. Worn volume of plasma nitrided samples of: (a) AISI 316, and (b) AISI 409, as a function of sliding distance.

The worn volumes were calculated based on Eq. 1 using the crater diameters. The volumetric wear curves of the nitrided AISI 316 sample (Fig. 4a) show that nitriding at 450°C presented a lower worn volume than at 500°C. As the pressure was increased (from 400 to 600Pa) the resistance against wear decreased. This inverse tendency is elucidated after observing Figure 5 and Table 2, which show two photomicrographs of a Brinell indentation on the nitrided AISI 316 sample and Brinell hardness values, respectively.

Brinell indentations on the AISI 316 samples nitrided at 450°C (Fig. 5a) and 500°C (Fig. 5b) under 600Pa, displayed in Fig. 5, shows that a crack network is produced around the indentation, for the nitriding temperature of 500°C, which is an evidence of higher fragility than that indentation performed on the sample nitrided at 450°C.

Increasing the nitriding temperature from 450°C to 500°C caused an increment on hardness (Tab. 2) and also an increase on the layer fragility (Figs. 5a and 5b). During the sphere sliding on wear testing, a fragile layer will generate a greater amount of wear debris, which in turn causes acceleration in the wear process. The plasma nitriding of the AISI 316 sample at 500°C resulted in different layer constituents compared to the treatment done at 450°C (Figs. 1b and 1a, and Fig. 2a) with distinct properties, which yielded different tribological behaviors.

Wear curves of the ferritic stainless steel (Fig. 4b) showed that with the increase of both nitriding temperature and pressure, the wear resistance improved. Thus the volume lost decreased as temperature and pressure raised, and also as hardness increased (Tab. 2). Since the layers produced at 450 and 500°C are mainly composed by the same compounds (Figs. 1d and 1e, and Fig. 2b), their wear behavior follows a natural and logic tendency. A harder layer results in a better performance.

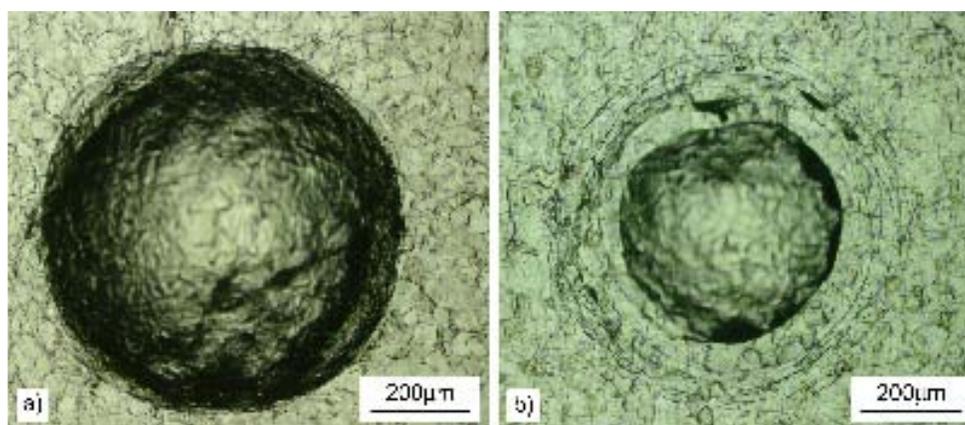

**Figure 5.** Brinell indentation on plasma nitrided samples of: (a) AISI 316 at 450°C, (b) AISI 316 at 500°C, (c) AISI 409 at 450°C and (d) AISI 409 at 500°C. 600Pa.


Table 2 also lists the layer thicknesses (e) and the wear scar depths after 20 min (800m) of wear testing obtained for each nitriding condition for 400 and 600Pa, and for the untreated AISI 316 and 409 samples, for comparison purposes. The h values were obtained based on Eq. 2.

Comparing the layer thicknesses (e) and the scar depths (h) after 800m of wear testing for all nitrided samples, it can be noted that all tests did not perforate the layer, except for the AISI 316 sample plasma nitriding at 450°C under 600Pa.

**Table 2.** Scar depth (h) after 20min of wear testing, nitriding layer thickness (e) and Brinell hardness (HB)

Sample	h (µm) – 20min	e (µm)	HB
<b>AISI 316</b>	26±1	---	147±3
<b>AISI 316 450°C/400Pa</b>	10.9±0.5	14.9±0.9	180±11
<b>AISI 316 450°C/600Pa</b>	11.6±0.7	9.4±0.8	188±8
<b>AISI 316 500°C/400Pa</b>	14.4±0.2	34±2	313±14
<b>AISI 316 500°C/600Pa</b>	18.9±0.3	29±2	444±8
<b>AISI 409</b>	125±2	---	188±9
<b>AISI 409 450°C/400Pa</b>	17.4±0.5	29±2	242±11
<b>AISI 409 450°C/600Pa</b>	15.6±0.3	20±2	246±20
<b>AISI 409 500°C/400Pa</b>	10.2±0.4	72±2	291±3
<b>AISI 409 500°C/600Pa</b>	11.9±0.5	68±2	353±23

Figure 6 shows the worn volumes which occurred at the end of the wear tests carried out on nitrided layers and the substrates, for comparison purposes. Worn volume of the AISI 409 steel sample (Fig. 6b) is around 20 times greater than that observed for the AISI 316 one (Fig. 6a).

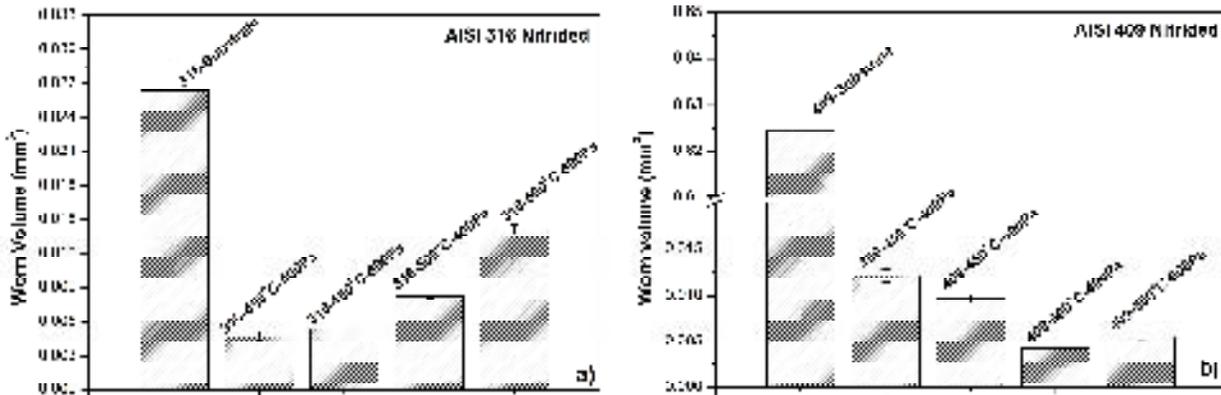

**Figure 6.** Worn volumes after 800m of wear testing of the a) AISI 316 and b) AISI 409 plasma nitrided samples, and the substrates.

The worn volumes after 800m of sliding are plotted in bars and show that for the nitrided steel samples the maximum volume lost value was about 0.015mm<sup>3</sup>, which is 2 times lesser than the observed for the AISI 316 substrate and 40 times lesser than the observed for the AISI 409 substrate. This confirms that the plasma nitriding treatment is effective regarding wear resistance.

## 4 CONCLUSIONS

Plasma nitriding treatment on the austenitic (AISI 316) and ferritic (AISI 409) stainless steels produced continuous and homogeneous layers. The nitrided AISI 316 sample presented expanded austenite layers, for the treatment temperature of 450°C, and layers having chromium nitrides (CrN and Cr<sub>2</sub>N), for the treatment temperature of 500°C. Nitriding the AISI 409 sample yielded similar layers for both treatment temperatures, mainly chromium (Cr<sub>2</sub>N) and iron (Fe<sub>2</sub>N, Fe<sub>3</sub>N, and Fe<sub>4</sub>N) nitrides. The layer thickness increased as the temperature was raised. An inverse effect was

observed for the layer thickness in respect to the pressure. The surface hardness of the nitrided steels increased as the treatment temperature and pressure were raised.

The AISI 316 substrate steel showed a better wear performance than the AISI 409 one. After plasma nitriding, the AISI 316 steel yielded higher wear resistance for lower treatment temperature and pressure. The increase in layer fragility, for higher temperatures and pressures, observed for the nitrided AISI 316 samples, was responsible for this inverse tendency.

The wear resistance of the nitrided AISI 409 sample followed a logic tendency: the harder the layer, the better the performance. In other words, the performance was improved with the increase of both temperature and pressure.

## Acknowledgments

The authors would like to thank CAPES, for the scholarships granted to F.A.P. Fernandes, S.C.Heck, and R.G. Pereira, CNPq and FAPESP, for financial assistance.

## REFERENCES

- 1 LO, K.H., SHEK, C.H., LAI, J.K.L. Recent developments in stainless steels. *Materials Science and Engineering R*, v. 65, p. 39-104, 2009.
- 2 PECKNER, D., BERNSTEIN, I.M. (Eds.), *Handbook of Stainless Steels*, McGraw-Hill Inc., 1977.
- 3 MENTHE, E., RIE, K.-T., SCHULTZE, J.W., SIMSON, S. Structure and properties of plasma-nitrided stainless steel. *Surface and Coatings Technology*, v. 74-75, p. 412-416, 1995.
- 4 FERNANDES, F.A.P., HECK, S.C., PEREIRA, R.G., PICON, C.A., NASCENTE, P.A.P., CASTELETTI, L.C. Ion nitriding of a superaustenitic stainless steel: Wear and corrosion characterization. *Surface and Coatings Technology*, in press article, 2010.
- 5 FEWELL, M.P., PRIEST, J.M., BALDWIN, M.J., COLLINS, G.A., SHORT, K.T. Nitriding at low temperature. *Surface and Coatings Technology*, 131 (2000) 284-290.
- 6 MENTHE, E., RIE, K.-T. Further investigation of the structure and properties of austenitic stainless steel after plasma nitriding. *Surface and Coatings Technology*, v. 116-119, p. 199-, 1999.
- 7 PRANEVICIUS, L., TEMPLIER, C., RIVIERE, J.-P. On the mechanism of ion nitriding of an austenitic stainless steel. *Surface and Coatings Technology*, v. 135, p. 250-, 2001.
- 8 PICARD, S., MEMET, J.B., SABOT, R. Corrosion behaviour, microhardness and surface characterisation of low energy, high current ion implanted austenitic stainless steel. *Materials Science and Engineering A*, v. 303, p. 163-172, 2001.
- 9 MENTHE, E., BULAK, A., OLFE, J., ZIMMERMANN, A., RIE, K.-T. Improvement of the mechanical properties of austenitic stainless steel after plasma nitriding. *Surface and Coatings Technology*, v. 133-134, p. 259-263, 2000.
- 10 RIVIÈRE, J.P., TEMPLIER, C., DECLÉMY, A., REDJDAL, O., CHUMLYAKOV, Y., ABRASONIS, G. Microstructure of expanded austenite in ion-nitrided AISI 316L single crystals. *Surface and Coatings Technology*, v. 201, p. 8210-8214, 2007.
- 11 FERNANDES, F.A.P., LOMBARDI-NETO, A., CASTELETTI, L.C., DE OLIVEIRA, A.M., TOTTEN, G.E. *Heat Treating Progress*, jul/aug, p. 41-43, 2008.
- 12 DONG, H. S-phase surface engineering of Fe-Cr, Co-Cr and Ni-Cr alloys. *International Materials Reviews*, v. 55, p. 65-98, 2010.

- 13 XU, X.L., WANG, L., YU, Z.W., HEI, Z.K. Microstructural characterization of plasma nitrided austenitic stainless steel. *Surface and Coatings Technology*, v. 132, p. 270-274, 2000.
- 14 RUTHERFORD, K.L; HUTCHINGS, I.M. Theory and application of a micro-scale abrasive wear test. *Journal of Testing and Evaluation*, v.25, n.2, p.250, 1997.
- 15 RUTHERFORD, K.L; HUTCHINGS, I.M. A micro-abrasive wear test, with particular application to coated systems. *Surface and Coatings Technology*, v. 79, p. 231-239, 1996.